

Influence of dissolved oxygen on the bioleaching efficiency under oxygen enriched atmosphere

Anne-Gwenaëlle Guezennec, Catherine Joulian, Jérôme Jacob, Anas Archane, Dominique Ibarra, Raphaëlle Gregory, Françoise Bodénan, Patrick d'Hugues

► **To cite this version:**

Anne-Gwenaëlle Guezennec, Catherine Joulian, Jérôme Jacob, Anas Archane, Dominique Ibarra, et al.. Influence of dissolved oxygen on the bioleaching efficiency under oxygen enriched atmosphere. Minerals Engineering, Elsevier, 2017, 10.1016/j.mineng.2016.10.016 . hal-01427774

HAL Id: hal-01427774

<https://hal-brgm.archives-ouvertes.fr/hal-01427774>

Submitted on 6 Jan 2017

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Influence of dissolved oxygen on the bioleaching efficiency under oxygen enriched atmosphere

Anne-Gwénaëlle Guezennec^{1*}, C. Jouliau¹, J. Jacob¹, A. Archane², D. Ibarra³, R. Gregory³, F. Bodénan¹, P. d'Hugues¹

¹ BRGM -Water, Environment & Ecotechnologies Division, 3, av. Claude Guillemin, BP 36009, 45060 Orléans Cedex 2, France - +33 (0)2 38 64 31 36, a.guezennec@brgm.fr

²Milton Roy Mixing, 10 rue du Bois Gasseau, 77210 Samoreau, France


³Air Liquide, CRCD, 1 chemin de la porte des Loges, BP 126, 78354 Jouy en Josas, France

ABSTRACT


The use of oxygen enriched air is a common practice in high-temperature bioleaching tests (> 70°C) to overcome oxygen solubility limitation and reduced the energy costs of the process. Air is usually preferred in medium and low-temperature operations mainly for technical and economic constraints. Nevertheless, under high-sulfide loading conditions - high-grade metal sulfide concentrates and high solids concentration - the microbial and chemical demand for oxygen is significantly increased during the bioleaching process. If not satisfied, this high oxygen demand might limit the oxidation efficiency. Therefore it requires the injection of large amounts of air. Sparging with oxygen enriched gas instead of air may offer an interesting alternative process option to improve gas transfer in the bioleaching reactor and to provide an adequate oxygen supply in order to satisfy the oxygen demand. It might be useful to develop innovative alternative to the classical stirred tank reactor (STR) technology. However, the use of such conditions can lead to much higher dissolved oxygen (DO) concentrations than those encountered with air. Very few papers have been devoted to the study of the optimal range of DO concentrations for bioleaching processes. Most of them reported an inhibitory effect of DO concentrations above 5 ppm. The purpose of this study was to investigate the influence of DO on the bioleaching efficiency under oxygen-enriched atmosphere in 21 L stirred tank reactor at 42°C. Bioleaching experiments were performed in continuous mode with sulfide-rich tailings wastes composed mainly of pyrite (51%) and quartz using the "BRGM-KCC" bacterial consortia. The solid load was close to 20% (w/w). Using various oxygen supply conditions (partial pressure, gas rate), the DO concentration in the reactor varied between 4 and 17 ppm. For a DO ranging from 4 to 13 ppm, a good bacterial oxidizing activity was observed and the sulfide dissolution efficiency increased with the DO concentration. It is assumed that this improvement of the bioleaching efficiency was linked to an increase of the oxygen transfer rate from the gas phase to the liquid phase rather than a direct effect of the DO level. When the DO concentration reached 17 ppm a significant decrease of the microbial activity and consequently of the oxygen consumption was noticed. These results show that there is a critical value above which the DO concentration is detrimental to the activity of the bioleach microorganisms present in the "BRGM-KCC" consortia but this value is much higher than the one usually mentioned in the literature.

Key-words: bioleaching, oxygen, dissolved oxygen concentration, sulfide, bacteria monitoring, stirred tank reactor

Biohydrometallurgy is well established for the treatment of certain sulfide minerals, where iron and sulfur-oxidising bacteria are used for the leaching of low grade copper ores and the pretreatment of pyritic gold ores and concentrates. However part of the mining industry remains skeptical and reluctant to adopt biohydrometallurgical techniques as a reliable alternative option. Heap leaching is sometimes considered unsuitable due to space constraints, slow leaching kinetics and low recovery rate. The interest of using stirred tank reactor (STR) for the treatment of other minerals than refractory gold ores, such as the base metal sulfides, has already been demonstrated but some improvements are still needed to meet economic viability (d'Hugues *et al.*, 2008; Spolaore *et al.*, 2009 ; Kutschke *et al.* 2015). The main costs of bioleaching operations in STR are the costs associated with the leaching tanks and the gas mass transfer to the pulp. The main capital costs are the ones for the agitators and for the gas injection devices. The main operating costs are associated with the energy consumption required for slurry agitation and air compression, since air is usually used to provide oxygen in bioleaching operations (Rossi, 2001; Morin et d'Hugues, 2007; van Aswegen *et al.*, 2007). The microorganisms involved in bioleaching processes get their energy through the oxidation of reduced sulfur compounds and iron (II). In these reactions oxygen is used as electron acceptor. In the case of pyrite bioleaching mechanisms involve the following oxidation reactions:



The reactions (2) and (3) are biologically catalyzed by acidophilic Fe- and S-oxidizing bacteria, whereas the reaction (1) occurs through chemical oxidation. The combination of the three reactions leads to the overall bioleaching reaction (Eq. 4) which shows that 3.5 mols of oxygen is required to oxidize 1 mol of pyrite.



Oxygen supply is thus a key issue, particularly in bioleaching processes with high-sulfide loading conditions where the microbial and chemical demand for oxygen is significantly increased. As a consequence, there is a need to inject large amounts of air which can be technically difficult and increases the costs of the process. Sparging with oxygen enriched gas instead of air may offer an interesting alternative process option to improve gas transfer and bioleaching efficiency by providing an adequate oxygen supply in order to satisfy high oxygen demand.

Gas mass transfer in bacterial leaching systems has been widely studied and is well documented (Bailey and Hansford, 1993a; Bailey and Hansford, 1994; Boon and Heijnen, 1998; Savic *et al.*, 1998; Veglio *et al.*, 1998). Transfer to liquid theory (illustrated schematically in Fig. 4) indicates that the O_2 mass transfer rate, called R_{O_2} (quantity of oxygen transferred in liquid phase per unit of time) is given by:

$$R_{O_2} = K_{La} \times (C^* - C_L) \quad Eq. 5$$

where: R_{O_2} is O_2 transfer rate ($mol\ m^{-3}\ s^{-1}$)

K_{La} is the volumetric oxygen mass transfer coefficient (s^{-1})

C^* is the oxygen solubility in reactor conditions ($mol\ m^{-3}$)

C_L is the oxygen concentration in the liquid phase ($mol\ m^{-3}$)

Several authors (Lui *et al.*, 1987; Bailey and Hansford 1994; Jordan *et al.*, 1995; Myerson, 1981; Bailey and Hansford, 1993b) have pointed out that the lack of adequate gas mass transfer is a rate limiting step in many bacterial leaching processes. The gas-liquid mass transfer rate depends on a number factors (Van Weert *et al.*, 1995, d'Hugues *et al.*, 1997, Boon and Heijnen, 1998) such as the reactor type, geometry and size, the gas-flow rate, sparger design and depth, the stirring speed, particle shape and size, pulp density and viscosity. However oxygen can become a limiting factor in bacterial leaching

93 because of its low solubility: only 0.26 mM O₂ (8.32 ppm) can dissolve per liter of water at 25°C in an
94 air/water mixture. As mentioned by Witne and Phillips (2001), one way of increasing the solubility of
95 oxygen in water or media solution is by increasing the driving force, i.e. raising the oxygen partial
96 pressure in the gas stream supplied to the leach pulp. This mechanism is described by Henry's gas law
97 which gives the solubility of oxygen in solution in relation to the oxygen partial pressure in the gas
98 phase:

$$99 \quad C^* = (P^\circ/H) \quad \text{Eq. 6}$$

100 where: C^* is the oxygen concentration of the nutrient solution;

101 P° is the partial pressure of the gas in the gas phase;

102 H is Henry's constant, which is specific for the gas and the liquid phase.

103 Henry's gas law shows that the solubility of O₂ in the leach pulp increases with increasing oxygen
104 partial pressure in the gas stream. Higher O₂ partial pressures could be attained when the bioreactor
105 air or gas stream is enriched with added pure oxygen. This approach was used for the development of
106 processes using high thermophiles culture by teams working on the development of STR processes for
107 the bioleaching of chalcopyrite concentrates (Dew *et al.*, 1999; d'Hugues *et al.*, 2002). In these studies,
108 oxygen was used instead of air because of the low solubility of O₂ at high temperature. When working
109 with mesophilic or moderately thermophilic microorganisms, they might be various interests of using
110 O₂ enriched air such as (i) to decrease the flow of gas stream injected in the pulp, reducing energy
111 consumption linked to agitation and compression of air (ii) to improve gas transfer to satisfy higher
112 oxygen demand associated with higher sulfide concentration. Using O₂ enriched air is a promising
113 alternative that might be useful to develop innovation to improve the classical STR technology. Air
114 Liquide, Milton Roy Mixing and BRGM are currently testing an innovative bioleaching process using
115 floating agitators to mix and to suspend solids in the solution as well as to inject gases in the pulp.
116 This new concept enables to decrease the costs of bioleaching processes by operating in lagoons or
117 ponds instead of using costly tanks, and at higher solid loading (>20%) than in conventional stirred
118 tank bioreactors. In these conditions of high solid load, the microbial and chemical demand for oxygen
119 is significantly increased and air could be replaced by oxygen enriched gas to provide an adequate
120 oxygen supply in order to satisfy the oxygen demand.

121 However the use of such conditions can lead to much higher dissolved oxygen (DO) concentrations
122 than those encountered with air sparging. Very few papers have been devoted to the study of the
123 optimal range of DO concentrations for bioleaching processes. However most of them reported an
124 inhibitory effect of DO concentrations above 5 ppm (de Kock *et al.*, 2004; Wang *et al.*, 2015).

125 The purpose of this study was to investigate the influence of DO on the bioleaching efficiency of a
126 mesophile to moderate thermophile consortium. The bioleaching tests were carried out under oxygen-
127 enriched atmosphere in a 21L stirred tank reactor at 42°C in continuous mode with sulfide-rich
128 tailings wastes composed mainly of pyrite (51%) and quartz. The solid load was closed to 20% (w/w).
129 The DO concentration in the reactor was varied between 4 and 18 ppm by increasing the gas flow rate.
130 The influence of the DO level on the bioleaching efficiency was investigated through the monitoring of
131 the sulfide leaching kinetics, the sulfide dissolution yield and the structure and the abundance of the
132 microbial community.

133

134

2- MATERIALS AND METHODS

135

136 Characterization of the sulfidic materials

137 The experiments were performed using flotation tailings coming from a European copper mine. The
138 mineral of economic interest in the ore body is chalcopyrite (CuFeS₂). At site, the ore is ground and
139 valuable chalcopyrite is then separated from pyrite by flotation. Copper contained in the chalcopyrite
140 is recovered by smelting whereas pyrite is discharged in tailings, from which the material used in this

141 study was sampled. The tailings are mainly composed of pyrite (51%) containing cobalt (0.06%),
142 copper (0.19%) and gold (1 g/t). This waste has been chosen as test materials for its high content of
143 pyrite, which makes it particularly suitable for bioleaching.

144

145 **Bacterial culture and nutrients**

146 The experiments were carried out using the BRGM-KCC microbial consortium, which has already
147 been fully described (d'Hugues *et al.*, 2003). The predominant organisms in the culture are affiliated to
148 *Leptospirillum (L.) ferriphilum*, *Acidithiobacillus (At.) caldus* and *Sulfobacillus (S.) benefaciens*. The culture
149 used as an inoculum originated from BRGM stock culture, stored at -80 °C. The culture was
150 subcultured several times in batch mode from 2 mL up to 21 L prior to the beginning of the test. The
151 culture was grown in a nutrient medium called "0Km". This is a modified "9K" medium (9K without
152 iron, "m" indicating modification of the basal salts) and it was optimised for bacterial growth on
153 cobaltiferous pyrites. Its standard composition is the following: (NH₄)₂SO₄, 3.70 g L⁻¹; H₃PO₄, 0.80 g L⁻¹;
154 MgSO₄•7H₂O, 0.52 g L⁻¹; KOH, 0.48 g L⁻¹.

155

156 **Laboratory apparatus and experimental conditions**

157 Bioleaching tests were carried out in continuous mode using a 21 L (working capacity) laboratory-
158 scale stirred tank. This tank is made from 316L stainless-steel and has a height/diameter ratio equal to
159 1. The top of the reactors was connected to a gas cooling system to prevent excessive evaporation. The
160 bioleach slurry was mechanically stirred by a mixed (axial/radial) system (so-called BROGIM® –
161 BRGM/MRM) mounted on a rotating shaft. The gas stream made of N₂, CO₂ and O₂ supplied by Air
162 Liquide gas cylinder was injected beneath the turbine at the bottom of the reactor via a stainless steel
163 pipe. Gas mixture composition was controlled by valves and mass flow regulators for each gas. Gases
164 went through a gas mixer before injection in the reactor. The feed was made up of a high density pulp
165 flow (40% wt/wt of sulfidic materials in water) and a concentrated nutrient medium flow. The two
166 feed flows were pumped separately and injected into the tank in a ratio corresponding to the solids
167 ratio (20% w/w) required for the feeding pulp. The combination of the two flows resulted in nutrient
168 concentrations corresponding to 0Km medium. The residence time of the pulp in the tank was closed
169 to 2.2 days. The pH was regulated between 1.2 and 1.5 by adding limestone slurry of 500 g L⁻¹ CaCO₃.
170 The standard temperature was 42°C and was maintained constant by circulating cold water through
171 an internal stainless-steel coil.

172 Five conditions of gas flow rates and compositions were tested (Table 1). CO₂ was maintained close to
173 1% during the whole assay. O₂ partial pressure was first set to 56% and the gas flow rate was
174 progressively increased from 50 to 500 NL h⁻¹ (conditions 1 to 4, see Table 1) in order to increase the
175 concentration of dissolved oxygen in the liquid phase. In the last condition the gas flow rate was
176 decreased to 250 NL h⁻¹ and the oxygen partial pressure was set to 70%. For each condition, the
177 experiment was carried out for an average time of 20 days, which enabled to monitor the bioleaching
178 test during several residence times and reach a steady state.

179

180 **Table 1: Main operating conditions for the gas injection (the partial pressures are measured in the gas inlet**
181 **after mixing of the N₂, O₂ and CO₂ streams)**

	Gas flow rate	O ₂ partial pressure	CO ₂ partial pressure
	NL h ⁻¹	%	%
<i>Condition 1</i>	50	57.4	1.10
<i>Condition 2</i>	100	56.9	1.10
<i>Condition 3</i>	250	55.4	0.99
<i>Condition 4</i>	500	57.1	1.12

Condition 5	250	70	1.0
-------------	-----	----	-----

182
183
184

Analytical techniques

Daily monitoring

185 Electrochemical potential, pH and dissolved oxygen (DO) were measured directly in the pulp.
186 Samples of pulp were collected daily in the bioreactor and filtered (syringe filters in cellulose acetate,
187 diameter 30 mm, porosity 0.45 µm). Cobalt and total iron concentrations were measured by atomic
188 absorption spectroscopy (Varian SpectrAA-300) in the filtered fraction. The O₂ and CO₂ concentrations
189 in the inlet and outlet gas of the reactor were measured using a paramagnetic analyser and an infrared
190 analyser (ADC 7000 – Analytical Development Company Ltd.) respectively. The gas balancing
191 method was used to calculate the oxygen uptake rate (OUR). The oxygen transfer rate (OTR) and the
192 OUR are linked by the following equation:
193

$$194 \quad OTR = OUR + \frac{dC_{O_2}}{dt} = \frac{Q_{O_2}^{in} - Q_{O_2}^{out}}{V} \quad Eq. 7$$

195 where: dC_{O_2}/dt is the accumulation oxygen rate in the liquid phase,
196 $Q_{O_2}^{in}$ and $Q_{O_2}^{out}$ are the oxygen gas flow at the bioreactor inlet and outlet,
197 V the volume of the liquid phase in the bioreactor.

198 At steady state, when the DO concentration is constant, there is no accumulation of oxygen in the
199 reactor and the OUR is equal to the OTR. Assuming that the nitrogen gas flow is the same at the inlet
200 and outlet of the reactor (i.e. is not consumed neither transferred to the liquid phase), Eq. 7 becomes:

$$201 \quad OTR = OUR = \frac{Q^m \left(P_{O_2}^{in} - \frac{P_{N_2}^{in}}{P_{N_2}^{out}} P_{O_2}^{out} \right)}{V} \quad Eq. 8$$

202 where: Q^m is the gas flow rate at the inlet of the bioreactor,
203 $P_{N_2}^{in}$ and $P_{N_2}^{out}$ are the partial pressure of nitrogen in the gas at the inlet and outlet of the
204 bioreactor.

Analysis of the solid fractions and mass balances

205 When the bioleaching reactor was operating at steady state, samples were collected from the
206 overflowing pulp at the exit of the reactor and from the initial pulp feed. The samples of pulp were
207 first filtered with a Büchner funnel to separate liquid and solid phases. The filtered solid material was
208 then rinsed with a sulfuric acid solution at pH 1.8 and dried. Representative aliquots of the dried
209 materials (<80 µm) were analysed for metal contents (namely Fe, Co, Cu), total carbon and sulfur
210 speciation. Major and trace metal contents were determined by ICP-AES (Inductively Coupled
211 Plasma-Atomic Emission Spectrometry) after oxidizing digestion according to protocols dedicated to
212 ore analysis (degradation of all sulfides). Total carbon and total sulfur were determined using a Leco
213 analyzer: i.e. non-dispersive infrared analysis of CO₂ and SO₂ gas respectively, after heating and
214 passing of an oxygen stream. The same technique was used for sulfide (S²⁻) determination, once the
215 sample has been leached in warm sodium carbonate solution to convert the metal sulfate into
216 insoluble carbonates and soluble sulfate. Sulfate was determined by gravimetry after the sample being
217 leached at boiling temperature with a sodium carbonate solution, ferric ion reduced to ferrous iron by
218 the addition of hydroxylamine hydrochloride, and the filtrate being precipitated with barium
219 chloride. The analytical data were then used to calculate the mass balance of the operation and to
220 assess the bioleaching performances (sulfide oxidation rates and yields).
221

Bacterial community monitoring

222 Homogeneous 2 mL pulp samples were taken at the end of the steady state of each of the five
223 operating conditions. After centrifugation, the pellet was washed in Tris buffer (100 mM, pH 8) until
224 acidity was neutralized, and genomic DNAs were extracted with the FastDNA Spin Kit for Soil and
225 manufacturer's protocol (MP Biomedicals), except for a speed of 5 for 30 s for mechanical lyses. DNA
226

was also extracted with the same procedure from filtrate (2 mL) and solids (about 0.7 g) obtained after filtration of homogeneous pulp, in order to characterize bacteria located in the liquid phase or associated with the solids. The abundance of each inoculated strains, *i.e.* *L. ferriphilum*, *At. caldus*, and *S. benefaciens*, was determined by measuring abundance of their 16S rRNA gene using species-specific real-time quantitative PCR (qPCR) performed with the newly developed assays described by Hedrich *et al.* (2016). Results were expressed as numbers of gene copies per mL of bioleaching pulp.

3- RESULTS

3.1- Influence of the dissolved oxygen on the dissolution rate and the OUR


The oxygen partial pressures analyzed in the gas inlet and outlet for the five tested conditions and the corresponding oxygen solubility calculated using Henry's law (Eq. 6) are gathered in Table 2. This table presents also the DO concentration measured in the reactor. The gas injection conditions selected enabled to test a wide DO concentration range from 4.7 ppm to 17.7 ppm.

Table 2: Oxygen concentration in the gas phase and in the liquid phase in continuous pyrite bioleaching experiments (O₂ partial pressure measured in the gas inlet (P_{O₂ in}) and outlet (P_{O₂ out}) and corresponding O₂ solubility calculated using Henry's law; DO concentration measured in the reactor)

	P _{O₂ in}	O ₂ solubility* corresponding to P _{O₂ in}	P _{O₂ out}	O ₂ solubility* corresponding to P _{O₂ out}	measured DO concentration
	%	ppm	%	ppm	ppm
<i>Condition 1</i>	57.4	17.6	41.1	12.6	4.7
<i>Condition 2</i>	56.9	17.5	48.3	14.8	5.0
<i>Condition 3</i>	55.4	17.0	51.7	15.9	9.5
<i>Condition 4</i>	57.1	17.5	55.2	16.9	12.9
<i>Condition 5</i>	70	21.8	69	21.3	17.7

The variation in OUR and pyrite dissolution rate for the five tested conditions is shown in Fig. 1. Both increased when the DO concentration is increased from 4.7 ppm to 12.9 ppm, which corresponds to the conditions 1 to 4. OUR values are close to the values of pyrite dissolution rate as expected from Eq. 4 which shows that the bioleaching of 1 kg of pyrite consumes 1 kg of oxygen.

For the condition 5 where the DO concentration reached 17.7 ppm a sharp decrease of the pyrite dissolution rate was observed. In that case it was not possible to calculate the corresponding OUR because of the lack of precision in the analysis of the gas composition.

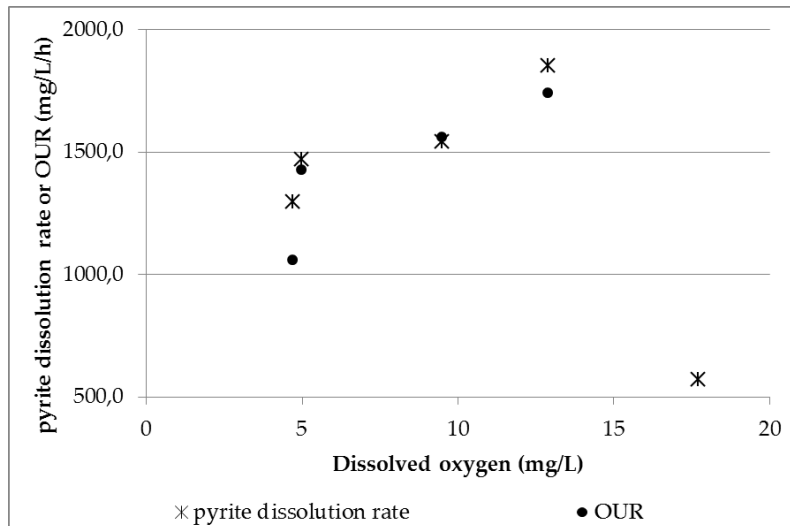

255

256 **Figure1: Pyrite dissolution rate and OUR vs. DO concentration in continuous pyrite bioleaching experiments**

257

258 **3.2- Influence of the dissolved oxygen on the dissolution yields**

259 In table 3 are reported the sulfide dissolution yields obtained for each tested conditions and the
 260 corresponding residence time. The slight variation in residence time can be explained by variation in
 261 the pumps flows for the calcite as it varies with the leaching efficiency and the corresponding
 262 production of sulfuric acid (see Eq. 4). It explains why the residence time is not constant especially for
 263 the conditions 1 and 5 for which the oxidizing activity was lower (as shown by the lower values of
 264 OUR). In both cases the amount of calcite introduced in the reactor was much lower and the residence
 265 time increased.

266

267

Table 3: Residence time and sulfide dissolution yield

	measured DO concentration	Residence time	Sulfide dissolution yield
	<i>ppm</i>	<i>d</i>	<i>%</i>
<i>Condition 1</i>	4.7	2.5	63%
<i>Condition 2</i>	5.0	2.2	56%
<i>Condition 3</i>	9.5	2.2	61%
<i>Condition 4</i>	12.9	2.2	77%
<i>Condition 5</i>	17.7	2.4	29%

268

269 When looking at the conditions 2, 3 and 4 for which the residence time is the same, the sulfide
 270 dissolution yield increased with the DO concentration. For the condition 4 the sulfide dissolution yield
 271 reached 77% for a DO concentration of 12.9 ppm. These results as well as the corresponding values of
 272 OUR and pyrite dissolution rates show (i) that the oxidizing activity in the bioleaching reactor is high
 273 from 5 to 12.9 ppm DO concentration and (ii) this activity is enhanced when the DO concentration
 274 increases.

275 For the condition 1 the sulfide dissolution yield is higher than for the conditions 2 and 3. But it is likely
 276 that this result is linked to the higher residence time in the reactor rather than to an effect of the DO
 277 considering the OUR and the pyrite dissolution rate which are both lower for the condition 1 than for
 278 the conditions 2 and 3. For the condition 5 the sulfide dissolution yield drops to 29% despite the

279 higher residence time. This result is in accordance with the decrease of pyrite dissolution rate
280 observed for this condition and seems to confirm the appearance of an inhibitory effect of the DO
281 concentration on the biological activity when the DO becomes too high.


282

283 3.3- Influence of the dissolved oxygen on the microbial community (abundance and structure)

284 The bacterial community composition shows that the strains present in the bioleach pulp were the
285 same as the three main strains which make up the BRGM-KCC consortium used to inoculate the
286 bioreactors. They are all found in the five tested condition, *L. ferriphilum* being dominant and
287 accounting for up to 80% of the total community (Fig 2).

288 The influence of DO on the biomass was studied, using 16S rRNA gene abundances as a measure of
289 total biomass as well as strain specific abundances. The total biomass was negatively affected by an
290 increase of DO, as shown by the decrease especially marked at a DO of 17.7 ppm where about one log
291 of gene copy numbers was lost (Fig. 2). The strains composing the community followed the same
292 trend. Especially, *At. caldus* abundance, although high at low DO (4.7 and 5 ppm), showed a regular
293 diminution all along the experiment as well as the sharper decrease (1 log) as soon as DO increased
294 from 5 to 9.5 ppm. Interestingly, *At. caldus* represented the large majority of planktonic bacteria
295 recovered from the liquid compartment (see Fig. 3) and accounted for more than 96% of the total
296 planktonic community at DO of 4.7 and 5 ppm, respectively. At 17.7 ppm however, the biomass of all
297 strains had decreased, and *L. ferriphilum* and *S. benefaciens* appeared to be only slightly less affected
298 (1.9 log between conditions 1 and 5) than *At. caldus* (2.3 log).

299

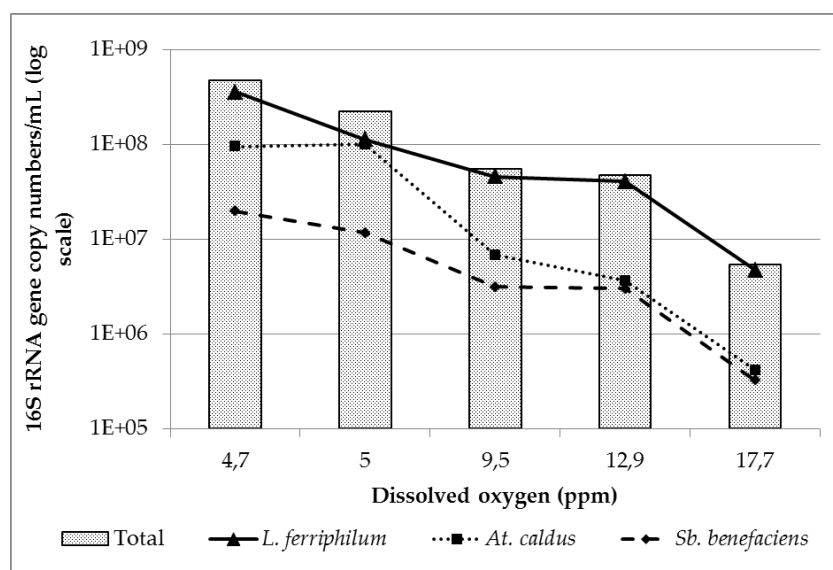

300

301 **Figure 2: Influence of DO concentration on the microbial community structure and the quantity of biomass**
302 **present in the reactor (assessed using the number of 16S rRNA gene copy)**

303

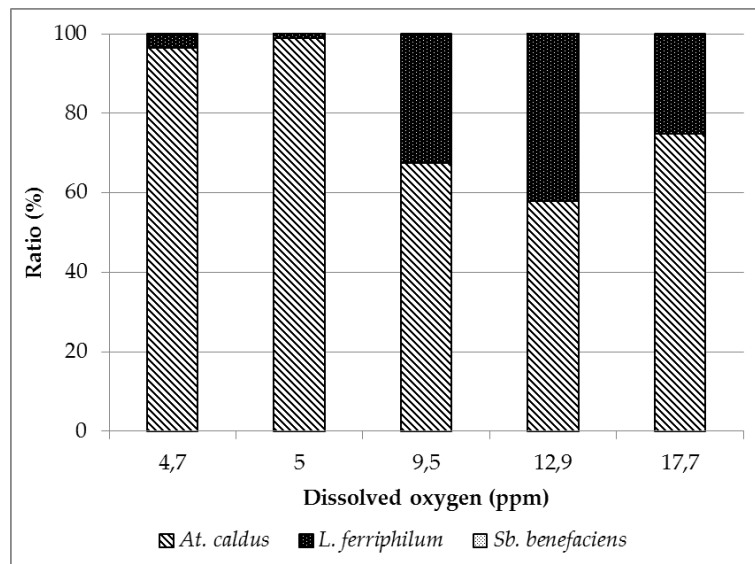


Figure 3: Structure of the microbial community in the liquid compartment

DISCUSSION

It is likely that a dissolved oxygen concentration between 13 and 17 ppm is critical for the bioleaching efficiency. Below this critical value bioleaching efficiency increases with the DO concentration. It is assumed that this improvement of the bioleaching efficiency is linked to an increase of the oxygen transfer rate from the gas phase to the liquid phase rather than a direct effect of the DO level. This hypothesis is partially confirmed by the increase of the oxygen uptake rate which is equal to the oxygen transfer rate in steady state mode. Above this critical value the DO concentration starts to be detrimental to the microbial activity and a sharp decrease of bioleaching efficiency (associated with a significant decrease of the bacterial population) is observed. This critical value is difficult to determine since the DO concentration depends on the rate of oxygen transferred from the gas phase to the liquid phase and from the oxygen consumed by the bio-oxidation. As soon as the DO concentration is above this critical value, the microbial activity decreases as well as the oxygen consumption, which entails an increase of the DO concentration.

The DO level which affects negatively the efficiency of bioleaching with the KCC consortium is quite different from those previously mentioned in the literature which reports an inhibitory effect for much lower DO levels. Especially this study can be compared to the results published recently by Wang *et al.* (2015) which studied the effect of dissolved oxygen on bioleaching using a sulfidic material and a microbial community similar to the ones used in this study. The optimum activity of the microbial population was obtained at 3.75 ppm concentration of DO. Above and below this value the OUR, the oxidation rate and the oxidation ratio decreased. It must be noted that Wang *et al.* carried out their experiments at 10% solids and in batch mode. The maximum OUR measured was closed to 160 mg L⁻¹ h⁻¹, which is more than ten times lower than the maximum OUR measured in this study. The microbial oxidizing activity was thus much lower. In the absence of data regarding the gas flow rate and its composition (especially the partial pressure of oxygen) it is difficult to explain the discrepancies observed between both studies, but it can be assumed that the influence of DO concentration on the bacterial activity is very dependent on the other operating conditions such as the solid concentration and the culture mode. It might also be bacterial strain dependent.

The increase of DO concentration has also a noticeable influence on the biomass which progressively decreases when the DO concentration increases. Below 13 ppm *At. caldus* seems to be the most affected by the increase of DO concentration. This might suggest that *At. caldus* is less tolerant to high DO concentrations than the other strains of the KCC consortium. Nevertheless other factors must also be


338 considered and especially the fact that *At. caldus* is the most abundant strain in the liquid phase
 339 compared to *L. ferriphilum* and *S. benefaciens* which are mainly located on the particles. Because of the
 340 presence of these bacteria on the solid phase it can be assumed that the oxidation of FeII and sulfur
 341 occur also at the surface of the pyrite particles. Oxygen is thus consumed at the liquid/solid interface
 342 and its transfer in the liquid/solid boundary layer is governed by the same theory as the one presented
 343 in the introduction:

344 $R_{O_2} = K_s \cdot a_s \cdot (C_L - C_s)$ Eq. 7

345 where: R_{O_2} is O_2 mass transfer rate ($\text{mol m}^{-3} \text{s}^{-1}$)
 346 K_s is the mass transfer coefficient (m s^{-1})
 347 a_s is the solid specific area (m^{-1})
 348 C_L is the oxygen concentration in the liquid phase (mol m^{-3})
 349 C_s is the oxygen concentration at the solid surface (mol m^{-3})

350 This phenomenon is illustrated in Fig. 4 and shows that the oxygen concentration in the liquid phase
 351 is higher than the one at the surface of the particles. The transfer rate being closely linked to the
 352 oxygen consumption in the system the difference (also called "driving force") is higher when the
 353 oxygen consumption rate increases. Planktonic cells are thus submitted to higher DO concentrations
 354 than the cells attached to the particles, which might explain that *At. caldus* abundance decreases more
 355 quickly than *L. ferriphilum* and *S. benefaciens*.

356

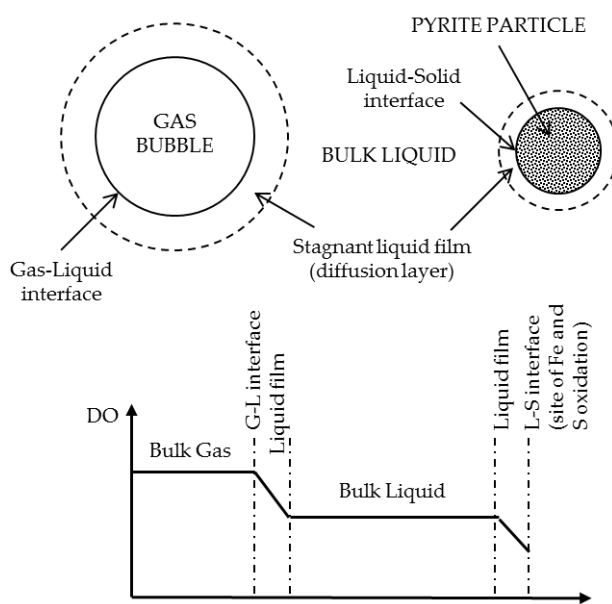

357
 358 **Figure 4: Schematic description of oxygen transfer and oxygen concentration profile in a triphasic media with**
 359 **reactions consuming oxygen at the solid surface**

360

361 The level of detrimental effect may also be linked to the capacity of a cell to handle high DO
 362 concentration. The toxicity of the oxygen towards the bacteria involved in bioleaching might be linked
 363 to the formation of reactive oxygen species (ROS) by a mechanism involving Fenton and Haber-Weiss
 364 reactions. By switching oxidation states metal ions further activate species like hydrogen peroxide
 365 (H_2O_2) and superoxide ($O_2^{\cdot-}$) to the highly reactive hydroxyl radical ($\cdot OH$) (Imlay, 2008). ROS are
 366 known to have deleterious effects on cells through a mechanism called oxidative stress (Halliwell
 367 2007). Several authors (Borda *et al.*, 2003; Cohn *et al.*, 2006; Schoonen *et al.*, 2006; Schoonen *et al.*, 2010)
 368 have shown that the oxidation of pyrite in solutions containing dissolved oxygen leads to the
 369 formation of ROS through several mechanisms that are synthetized in Fig. 5. As can be seen the ROS

370 concentration in the leaching solution would increase with the DO concentration. Recently,
 371 evaluations in tank reactors have also shown the negative influence of ROS generation (due to fine
 372 grinding of pyrite) on bioleaching (Jones *et al.*, 2011), suggesting the direct effect of external ROS
 373 generation on bioleaching organisms. Bioleaching bacteria harbor genetic systems for the defense
 374 against oxidative stress by the production of various proteins involved in anti-oxidative protection
 375 and biomolecules repair mechanisms (Cardenas *et al.*, 2012). If there is evidence that *Leptospirillum*,
 376 *Sulfobacillus* and *Acidithiobacillus* strains possess such systems, the mechanisms are not fully
 377 understood yet and their efficiencies depending on genus or strain during bioleaching are not known.

378

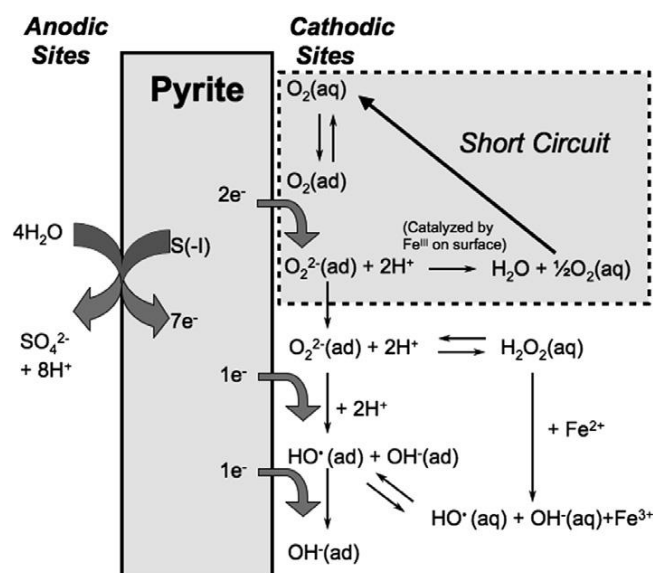


Figure 5: ROS formation mechanisms at pyrite surface (Schoonen *et al.* 2010)

379

380

381

382

383

CONCLUSION

384 The BRGM-KCC microbial consortium can tolerate DO levels up to 13 ppm, and probably higher level
 385 with a critical limit between 13 and 17.7 ppm, during continuous bioleaching and still maintain a high
 386 bioleaching activity. This value is much higher than the maximal DO levels reported in previous
 387 papers and is also higher than the solubility of oxygen in an air/water mixture (8.3 ppm at 25°C, 6
 388 ppm at 40°C). The bioleaching efficiency (oxidation rate and dissolution yield) increases with the
 389 increase of the oxygen supply (and oxygen transfer) up to a DO concentration of 13 ppm. However the
 390 microbial activity and consequently the oxygen consumption significantly decreased at DO
 391 concentration of 17 ppm. These results confirm the applicability of using oxygen enriched gas instead
 392 of air to efficiently supply oxygen in bioleaching reactors without inhibitory effect on the microbial
 393 oxidizing activity. However the oxygen partial pressure and the gas flow must be carefully adapted to
 394 the oxygen requirements of the system to avoid too high DO concentrations in the bioreactors.

395

396 Acknowledgments: This work is part of the collaborative bilateral research project Ecometals co-
 397 funded by the German Federal Ministry of Education and Research (BMBF under the grant ID
 398 033RF001) and the French National Research Agency (ANR-13-RMNP-0006). The authors thank
 399 M. Djemil, H. Tris for their technical involvement during the pilot operation.

400

401

REFERENCES

402

403

- 404 Bailey, A. D., and Hansford, G. S., (1993a). Factors affecting bio-oxidation of sulfide minerals at high
405 concentrations of solids: a review. *Biotechnology and Bioengineering*, 42(10), 1164-1174.
- 406 Bailey, A. D., and Hansford, G. S., (1993b). A fluidised bed reactor as a tool for the investigation of
407 oxygen availability on the bio-oxidation rate of sulphide minerals at high solids concentrations.
408 *Minerals Engineering*, 6(4), 387-396.
- 409 Bailey, A. D., and Hansford, G. S., (1994). Oxygen mass transfer limitation of batch bio-oxidation at
410 high solids concentration. *Minerals Engineering*, 7(2--3), 293-303.
- 411 Boon, M., and Heijnen, J. J., (1998). Gas-liquid mass transfer phenomena in bio-oxidation experiments
412 of sulphide minerals. A critical review of literature data, *Hydrometallurgy*, 48, 187-204.
- 413 Borda M. J., Elsetinow A. R., Strongin D. R. and Schoonen M. A. (2003) A mechanism for the
414 production of hydroxyl radical at surface defect sites on pyrite. *Geochimica et Cosmochimica Acta*
415 67, 935-939
- 416 Cárdenas, J. P., Moya, F., Covarrubias, M., Shmaryahu, A., Levicá, G., Holmes, D. S., and Quatrini, R.
417 (2012) Comparative genomics of the oxidative stress response in bioleaching microorganisms.
418 *Hydrometallurgy*, 127-128, 162-167.
- 419 Cohn A.C., Mueller S., Wimmer E., Leifer N., Greenbaum S., Strongin D.R. and Schoonen M.A.A
420 (2006) Pyrite-induced hydroxyl radical formation and its effect on nucleic acids. *Geochemical*
421 *Transactions* 7, 3.
- 422 d'Hugues, P., Cezac, P., Cabral, T., Battaglia, F., Truong-meyer, X. M., and Morin, D., (1997).
423 Bioleaching of a cobaltiferous pyrite: A continuous laboratory-scale study at high solids
424 concentration. *Minerals Engineering*, 10(55), 507-527.
- 425 d'Hugues, P., Foucher, S., Galle-Cavalloni, P., Morin, D., (2002). Continuous bioleaching of
426 chalcopyrite using a novel extremely thermophilic mixed culture. *International Journal of Mineral*
427 *Processing*, 66, 107-119.
- 428 d'Hugues, P., Battaglia-Brunet, F., Clarens, M., Morin, D. (2003). Microbial diversity of various metal-
429 sulfides bioleaching cultures grown under different operating conditions using 16S-rDNA
430 analysis. In: Tsezos, M., Remoudaki, E., Hatzikioseyan, A. (Eds.), *International*
431 *Biohydrometallurgy Symposium IBS 2003*. Hellas, Athens, 1313-1324
- 432 d'Hugues, P., Norris, P.R., Hallberg, K.B., Sanchez, F., Langwaldt, J., Grotowski, A., Chmielewski, T.,
433 Groudev, S. (2008). Bioshale FP6 European project: Exploiting black shale ores using
434 biotechnologies? *Minerals Engineering*, 21, 111-120.
- 435 de Kock, S.H., Barnard, P., du Plessis, C.A., (2004). Oxygen and carbon dioxide kinetic challenges for
436 thermophilic mineral bioleaching processes. *Biochemical Society Transactions*, 32, 273-275
- 437 Dew, D.W., Van Buuren, C., Mc Ewan, K., Bowker, C., (1999). Bioleaching of base metal sulphide
438 concentrates: a comparison of mesophile and thermophile bacterial cultures. In: Amils, R.,
439 Ballester, A. (Eds.), *Process Metallurgy 9A, Biohydrometallurgy and Environment Toward the*
440 *Mining of the 21st Century*. IBS' 99 Symposium. Elsevier, Amsterdam, The Netherlands, pp.
441 229- 238.
- 442 Halliwell, B., 2007. Biochemistry of oxidative stress. *Biochemical Society Transactions* 35 (5), 1147-
443 1150.
- 444 Imlay, J.A., 2008. Cellular defenses against superoxide and hydrogen peroxide. *Annual Review of*
445 *Biochemistry* 77, 755-776.
- 446 Hedrich, S., Guézennec, A.-G.G., Charron, M., Schippers, A. and Joulian, C. (2016) Development of
447 molecular assays to efficiently monitor and quantify microbial species during bioleaching of
448 copper-rich ores. *Biohydrometallurgy'16*, Falmouth (UK), June 20-22, 2016.

- 449 Jones G.C., Corin K.C., van Hille R.P., Harrison S.T.L. (2011) The generation of toxic reactive oxygen
450 species (ROS) from mechanically activated sulphide concentrates and its effect on thermophilic
451 bioleaching. *Minerals Engineering* 24, 1198–1208
- 452 Jordan, M.A., McGinness, S. and Phillips, C.V. (1995). Acidophilic bacteria, their potential mining and
453 environmental applications, *Minerals Engineering*, 9(2), 169-181.
- 454 Kutschke S., Guézennec A.G., Hedrich S., Schippers A., Borg G., Kamradt A., Gouin J., Giebner F.,
455 Schopf S., Schlömann M., Rahfeld A., Gutzmer J., P. D’Hugues, Pollmann K., Dirlich S.,
456 Bodéan F. (2015) Bioleaching of Kupferschiefer blackshale – A review including perspectives
457 of the Ecometals project. *Minerals Engineering* 75, 116–125
- 458 Lui, M. S., Brvaaiion, R.M.R., and Ducan., (1987). Oxygen transfer to *Thiobacillus* cultures, in:
459 *Biohydrometallurgy, Proceedings of International Symposium*, Warwick, P.R. Norris and D.P. Kelly
460 (eds.), Science & Technology Letters, Kew, Surrey, 375.
- 461 Myerson, A.S., (1981), Oxygen mass transfer requirements during the growth of *Thiobacillus*
462 *ferrooxidans* on iron pyrite. *Biotechnology and Bioengineering*, 23, 1413.
- 463 Rossi, G., The design of bioreactors. *Hydrometallurgy*, 59, 217-231.
- 464 Savic, D. S., Veljkovic, V. B., Lazic, M. L., Vrvic, M. M., and Vucetic, J. I., (1998). Effect of the oxygen
465 transfer rate on ferrous iron oxidation by *Thiobacillus ferrooxidans*., *Enzyme Microbiological*
466 *Technology*, 23, 427--431.
- 467 Schoonen, M.A.A, Cohn, C.A, Roemer, E., Laffers, R., Simon, S.R., O’Riordan, T., , (2006). Mineral-
468 Induced Formation of Reactive Oxygen Species. *Reviews in Mineralogy & Geochemistry*, 64, 179-
469 221.
- 470 Schoonen, M.A.A, Harrington, A.D., Laffers, R., Strongin, D.R., (2010). Role of hydrogen peroxide and
471 hydroxyl radical in pyrite oxidation by molecular oxygen. *Geochimica et Cosmochimica Acta*, 74,
472 4971–4987
- 473 Spolaore, P., Joulain, C., Gouin, J., Morin, D., & d’Hugues, P. (2009). Bioleaching of an organic-rich
474 polymetallic concentrate using stirred-tank technology. *Hydrometallurgy*, 99, 137-143.
- 475 Van Weert, G., Van Der Werff, D. and Derksen, J. J., (1995). Transfer of oxygen from air to mineral
476 slurries in a Rushton turbine agitated tank. *Minerals Engineering*, 8(10), 1109-1124.
- 477 Veglio, F., Beolchini, F., and Ubaldini, S., (1998). Empirical models for oxygen mass transfer: a
478 comparison between shake flask and lab-scale fermentor and application to manganese ore
479 bioleaching, *Process Biochemistry*, 33(4), 367-376.
- 480 Wang, H., Zhang, X., Zhu, M, Tan, W., (2015). Effects of dissolved oxygen and carbon dioxide under
481 oxygen-rich conditions on the biooxidation process of refractory gold concentrate and the
482 microbial community. *Minerals Engineering*, 80, 33-44.
- 483 Witne, J.Y. and Phillips, C.V., (2001). Bioleaching of Ok Tedi copper concentrate in oxygen- and carbon
484 dioxide enriched air. *Minerals Engineering*, 14 (1), 25–48.
- 485 Morin, D. and d’Hugues, P., Bioleaching of a cobalt-containing pyrite in stirred reactors: a case study
486 from laboratory scale to industrial application. In *Biomining*, ed. D.E. Rawlings and D.B.
487 Johnson. Springer-Verlag, Berlin Heidelberg, 2007, pp 35-56.
- 488 Van Aswegen, P.C., Van Niekerk, J. and Olivier, W., The BIOX process for the treatment of refractory
489 gold concentrates. In *Biomining*, ed. D.E. Rawlings and D.B. Johnson. Springer-Verlag, Berlin
490 Heidelberg, 2007, pp1-34.